

See discussions, stats, and author profiles for this publication at: <https://www.researchgate.net/publication/340348196>

High temperature oxidation and corrosion of spark plasma sintered FeCrAlTiY-10 mass% MoSi₂ coating on low carbon steel

Conference Paper in AIP Conference Proceedings · March 2020

DOI: 10.1063/5.0003163

CITATIONS

0

READS

64

6 authors, including:



B. Hermanto

Indonesian Institute of Sciences

37 PUBLICATIONS 66 CITATIONS

[SEE PROFILE](#)

High temperature oxidation and corrosion of spark plasma sintered FeCrAlTiY-10 mass% MoSi₂ coating on low carbon steel

Cite as: AIP Conference Proceedings **2221**, 110024 (2020); <https://doi.org/10.1063/5.0003163>

Published Online: 31 March 2020

Januaris Pane, Dedi Holden Simbolon, Bambang Hermanto, Kerista Sebayang, Marhaposan Situmorang, and Toto Sudiro



View Online



Export Citation

ARTICLES YOU MAY BE INTERESTED IN

[Improvement of carbon steel resistance against high temperature oxidation and corrosion by flame sprayed FeCrAlTiY-30 mass% CoNiCrAlY coating using N₂ pressure](#)

AIP Conference Proceedings **2221**, 110019 (2020); <https://doi.org/10.1063/5.0003155>

[The physico-mechanical properties of montmorillonite-filled natural rubber](#)

AIP Conference Proceedings **2221**, 030002 (2020); <https://doi.org/10.1063/5.0003861>

[The investigation of chemically deposited Cu₃BiS₃ into mesoporous TiO₂ films for the application of semiconductor-sensitized solar cells](#)

AIP Conference Proceedings **2221**, 030005 (2020); <https://doi.org/10.1063/5.0003105>

Lock-in Amplifiers

Find out more today



Zurich Instruments



High Temperature Oxidation and Corrosion of Spark Plasma Sintered FeCrAlTiY-10 Mass% MoSi₂ Coating on Low Carbon Steel

Januaris Pane^{1,3,a)}, Dedi Holden Simbolon^{1,4,b)}, Bambang Hermanto^{2,c)}, Kerista Sebayang^{1,d)}, Marhaposan Situmorang^{1,e)}, Toto Sudiro^{2,f)}

¹Postgraduate Program of Physics, Faculty of Mathematic and Natural Science, University Sumatera Utara, Jl. Bioteknologi No.1 Medan 20155-Indonesia

²Research Center for Physics, Indonesian Institute of Sciences, Kompleks PUSPIPTEK Serpong, Tangerang Selatan, Banten 15310-Indonesia

³Universitas HKBP Nommensen, Faculty of Teacher Training and Education, Jl. Sutomo No. 4A Medan 20234-Indonesia

⁴Universitas Quality, Faculty of Teacher Training and Education, Jl. Ngumban Surbakti No.18 Sempakata, 20132-Indonesia

^{a)}januarispane@students.usu.ac.id,

^{b)}dediholden@students.usu.ac.id,

^{c)}bamb046@lipi.go.id,

^{d)}keristasebayang@usu.ac.id,

^{e)}marhaposan@usu.ac.id,

^{f)}Corresponding author: toto011@lipi.go.id

Abstract. In the present study, we prepared the FeCrAlTiY-10 mass% MoSi₂ coating on low carbon steel using the spark plasma sintering (SPS) technique. Its resistance against oxidation and corrosion was studied in air and atmosphere containing 20 mass% NaCl at 700°C for 8 cycles. The results show that a dense coating layer is composed by FeCr containing Al and MoSi₂ phases. After high temperature oxidation test, a thin protective Al₂O₃ layer was formed. While mix oxide scales composing of (Cr,Fe)₂O₃, Al₂O₃, and Fe₃O₄ were formed after high temperature corrosion test. Although, the affected area after corrosion test was more severe than after oxidation test, the corroded sample somehow had a lower mass gain compared to oxidized sample after 8 cycles exposure. This could be related to the effect of chlorine ions and oxide spallation during cyclic corrosion test.

INTRODUCTION

Carbon steel metal material is widely used in many industries because it has several advantages, such as, high strength, good machining ability and low cost [1-2]. However, it has weaknesses on oxidation, corrosion and wear resistance, limiting its application under severe conditions. Accordingly, a protective coating is required for example to improve their oxidation and corrosion resistance.

MoSi₂ is a great attractive candidate material for the next generation high-temperature applications (600–1800°C) because it has high melting-point (2303 K), high strength and good thermal conductivity, relatively low density [3-6]. Therefore, it was considered for coating to protect the beneath materials from high temperature corrosion and oxidation. In addition, FeCrAlTiY has also been studied due to its resistance toward oxidation and corrosion at high temperature [7]. Modifying the coating or alloy material may lead the formation of a thin protective oxide scale.

Several studies have made efforts to improve the oxidation and corrosion resistance of materials by adding alloying elements and changing the coating methods in order to obtain maximum coating results. As a new kind of technology, spark plasma sintering (SPS) also known as field assisted sintering (FAST) or pulsed electric current sintering (PECS) has been proved to be applicable for synthesizing the metals, composites and ceramics under compressive pressure and continuous heating in vacuum. This technique has several advantages such as

The 1st International Conference on Physics and Applied Physics (The 1st ICP&AP) 2019

AIP Conf. Proc. 2221, 110024-1–110024-7; <https://doi.org/10.1063/5.0003163>

Published by AIP Publishing. 978-0-7354-1980-3/\$30.00

high efficiency, short sintering period, densification sintering, controllable coating thickness and a relatively low temperature [8-9]. Moreover, it is as a new method for coating fabrication with defined compositions and homogenous microstructures [10]. Beside that, SPS can prepare substances with high density [11].

In our previous work [12], we have studied the high temperature oxidation resistance of several compositions of flame sprayed FeCrAlTiY-x mass % MoSi₂ (x = 0, 10, 20 and 30) coatings on carbon steel. We found that the presence of defects such as pores, gap and cracks in the coating becomes major factors in affecting the sample oxidation. In addition, during coating preparation the use of compressed air as gas carrier leads to oxidation of coating elements. The results of study indicated that the FeCrAlTiY-10 mass% MoSi₂ coating showed a better oxidation resistance among the other coating composition. In order to improve the 10 mass% MoSi₂ coating structure, a spark plasma sintering technique was used to prepare the coating on the surface of carbon steel. In this study, we also investigated its oxidation and corrosion behaviour in air and atmosphere containing 20 mass% NaCl, respectively. The results are presented and discussed in this paper.

EXPERIMENTAL PROCEDURES

The substrate in this study is carbon steel ST 41 with a sample size of 10 mm × 10 mm × 3 mm. All the samples were mechanically ground in various grit of abrasive SiC papers and then ultrasonically degreased in ethanol solution. Before coating preparation, the sand blasting process is conducted with a pressure of 12 bar to increase the bonding of substrat and coating layer.

The powders of MoSi₂-Japan New Metals Co. Ltd. and FeCrAlTiY-Sandvik Materials Technology Ltd. were used in this study. The FeCrAlTiY with 10 mass% MoSi₂ content was selected as the coating composition. The carbon steel and powder coating were prepared in 20 mm of graphite dies. The substrate was burried with FeCrAlTiY-10 mass% MoSi₂ powder. Sebsequently, it was consolidated by a spark plasma sintering unit (DR. SINTER model SPS-625) at constant axial pressure of 30 MPa, heated from room temperature for up to 900°C in the evacuated chamber of less than 6 Pa.

After sample sintering and cleaning, the oxidation and corrosion resistance of the sample were studied in air and 20 mass% NaCl atmosphere at 700°C for 8 cycles by measuring the mass change of sample per unit area. The structure of 10 mass% MoSi₂ coating before and after high temperature oxidation and corrosion tests was analyzed using X-ray diffraction (XRD) and scanning electron microscope (SEM) attached with an energy dispersive X-ray spectrometer (EDX).

RESULTS AND DISCUSSIONS

Phase Composition and Microstructure of FeCrAlTiY-10 mass% MoSi₂ Coating

Figure 1 (a) shows the XRD pattern of FeCrAlTiY-10 mass% MoSi₂ coating deposited using Spark Plasma Sintering (SPS) technique on the surface of low carbon steel. The diffraction peaks of FeCrAlTiY-10 mass% MoSi₂ coating are detected as FeCr and MoSi₂ phases. There is no oxide formed due to that the sintering process with SPS is carried out in a vacuum condition (< 6 Pa), hindering the oxidation of coating elements. Fig. 1(b) shows cross-sectional microstructure at the coating/substrate interface. It can be seen that a very small fraction of pore can be observed.

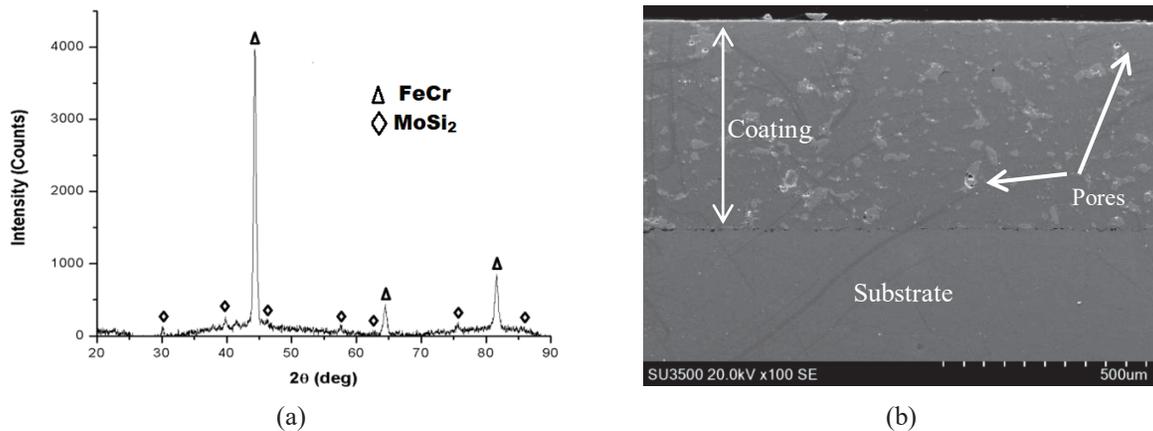


FIGURE 1. (a) XRD pattern and (b) SE-SEM cross-sectional microstructures of FeCrAlTiY-10 mass% MoSi₂ coating

Figure 2 shows the EDX element mapping of FeCrAlTiY-MoSi₂ coating after sintering at 900°C. The results show that the dominant coating elements are Fe (magenta color intensity), Cr (cyan color intensity), Mo (pink color intensity) and Si (red color intensity). Although the coating contains some amount of Al element, the Al distribution in the coating is not clearly observed. This could be due to fact that it is finely distributed in the coating layer. Moreover, it is important to note that no oxygen distribution is found in Fig. 2. This indicates that the oxidation during coating preparation does not occur. The detection of Fe, Cr, Mo, Si distribution in the coating supports the XRD analysis results which show that the coating is composed mainly of FeCr and MoSi₂ phases, as shown in Fig. 1(a).

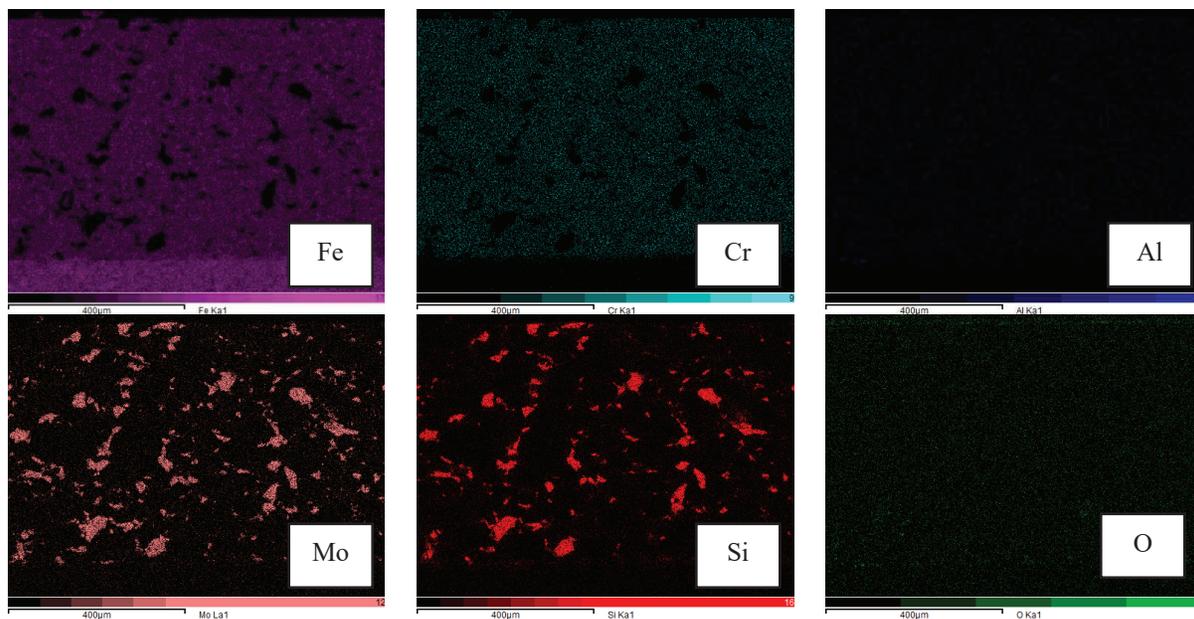


FIGURE 2. EDX elemental mapping of FeCrAlTiY-10 mass% MoSi₂ coating

Oxidation and Corrosion Kinetic

Figure 3 shows the mass gain curve per unit area of FeCrAlTiY coating with 10 mass% MoSi₂ after oxidation and corrosion test at 700°C for 8 cycles. In the initial stage, oxidation at high temperatures cause a rapid surface reaction which cause an increase in the rate of ion migration, resulting in the oxide layer formation [13] and an increase in mass gain of the sample. As shown in Fig. 3, the corroded sample has a lower mass gain compared to oxidized sample at 700°C for 8 cycles which is 0.029 mg/mm² and 0.237 mg/mm², respectively. It is interesting to note that for corroded sample, the mass gain increases in the first cycle of the test then decreases with the increase of cyclic corrosion time. This is probably due to the influence of chloride ions. Previous study reported that in the atmospheric condition, chloride ions seem to only work during the corrosion initiation and failed to penetrate through the thick rust layer at later stages, so that corrosion rates increased initially and then

declined with the exposure time in atmosphere [14]. Another reason is that some amount of corrosion products may spall out from the sample surface.

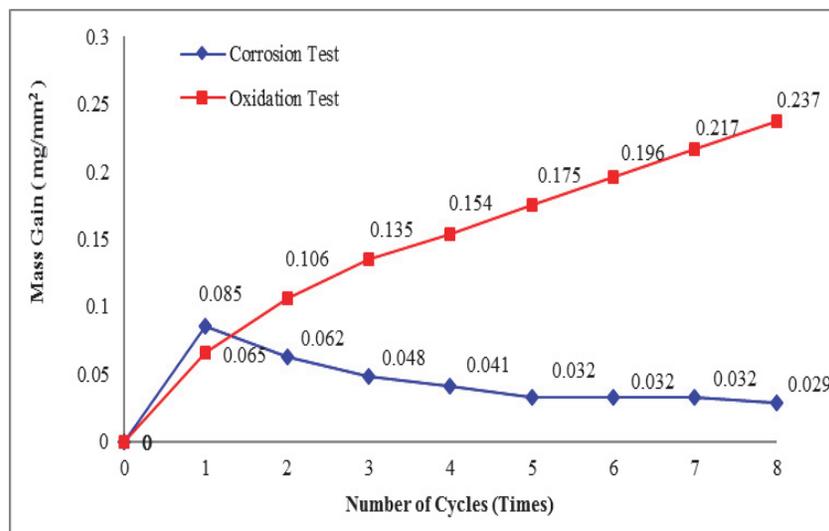


FIGURE 3. Mass gain curves of FeCrAlTiY coatings with 10 mass% MoSi₂ after oxidation and corrosion test at 700°C for 8 cycles

Phase Composition and Microstructure of Low Carbon Steel After Oxidation and Corrosion Test

Figure 4(a) shows the results of XRD analysis of FeCrAlTiY-10 mass% MoSi₂ coating after oxidation test at 700°C for 8 cycles. The results show that 3 phases namely FeCr, MoSi₂ and Al₂O₃ are confirmed from the sample reflection, suggesting that the oxidation product of this coating is mainly an Al₂O₃.

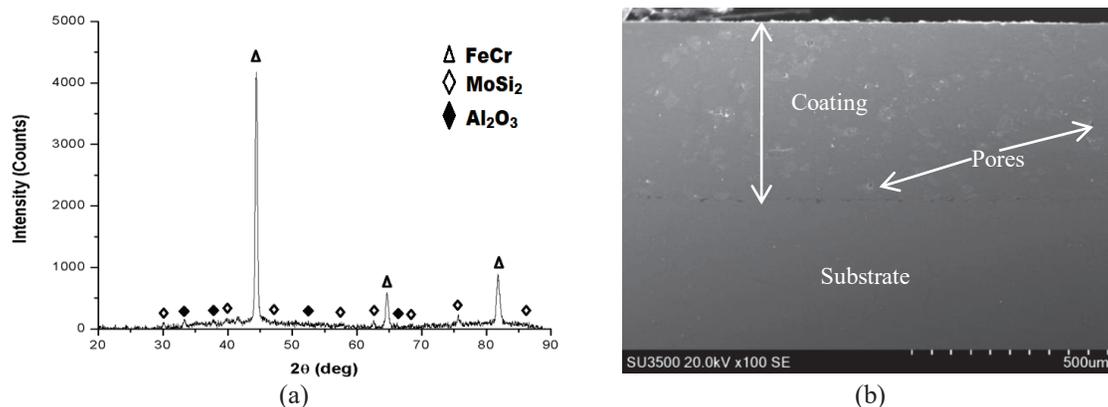


FIGURE 4. (a) XRD pattern and (b) SE-SEM cross-sectional microstructures of FeCrAlTiY-10 mass% MoSi₂ coating after oxidation test at 700°C for 8 cycles

The cross-sectional microstructures of the coating after high temperature oxidation test are given in Fig 4(b). Visually, no significance different is found in the coating after and before oxidation test (Fig. 1(b)). However, EDX elemental maps of oxidized sample as shown in Fig. 5 clearly show the fine distribution of Al and O in the external layer. This result is in good agreement with the result of XRD analysis, as shown in Fig. 4(a) which is confirming that the fine distribution of Al and O must be Al₂O₃ layer. This thin oxide layer can acts as protective barrier for oxygen inward diffusion.

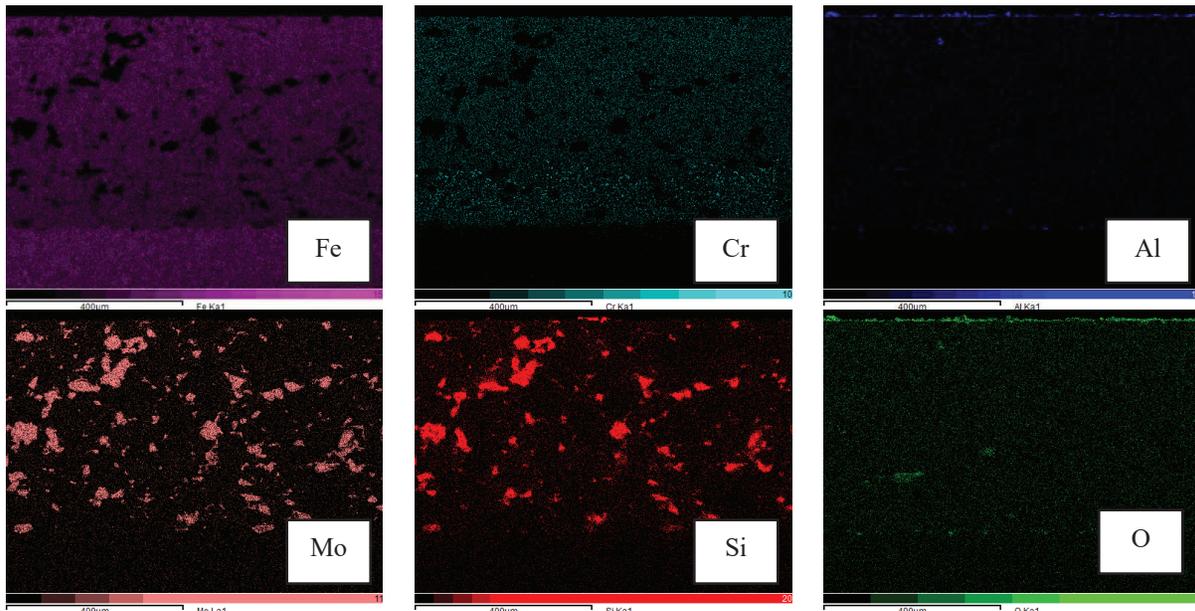


FIGURE 5. EDX elemental mapping of FeCrAlTiY-10 mass% MoSi₂ coating after oxidation test at 700°C for 8 cycles

Figures 6 (a) and (b) show the XRD pattern and typical SE-SEM cross-sectional microstructure of FeCrAlTiY-MoSi₂ coating on low carbon steel after corrosion test in air at 700°C for 8 cycles, respectively. As shown in Fig. 6(a), the peaks reflection after high temperature corrosion test corresponds to FeCr, (Cr,Fe)₂O₃, Al₂O₃, and Fe₃O₄.

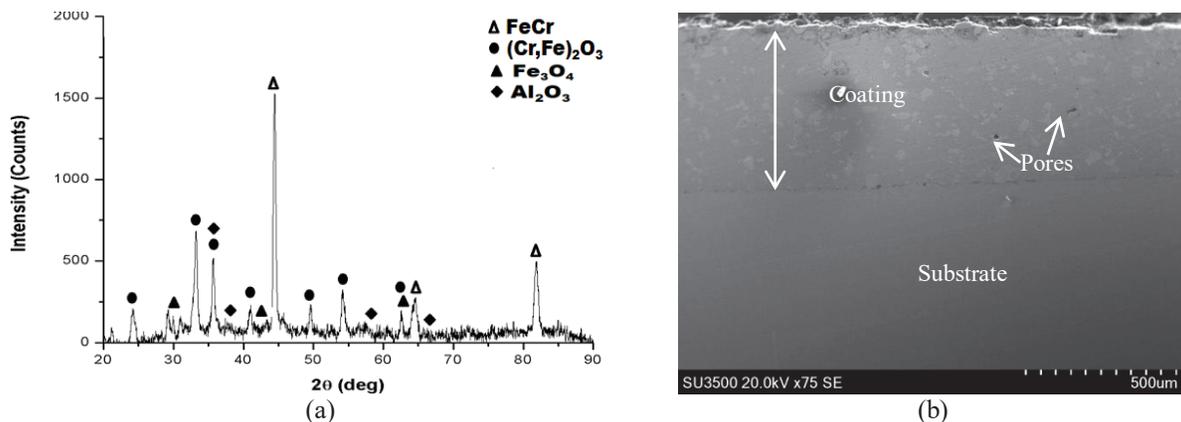


FIGURE 6. (a) XRD pattern and (b) SE-SEM cross-sectional microstructures of FeCrAlTiY-10 mass% MoSi₂ coating after corrosion test at 700°C for 8 cycles

Figure 7 shows the result of EDX element mapping of FeCrAlTiY-10 mass% MoSi₂ coating after corrosion test. The magenta, cyan, pink, red, blue and green color intensities correspond to Fe, Cr, Mo, Si, Al and O distribution, respectively. The EDX elemental maps clearly indicate the distribution of Fe, Cr, Al and O on the coating surface. This results supports the XRD analysis which determine the corrosion products composing of (Cr,Fe)₂O₃, Fe₃O₄ and Al₂O₃ as shown in Fig. 6(a).

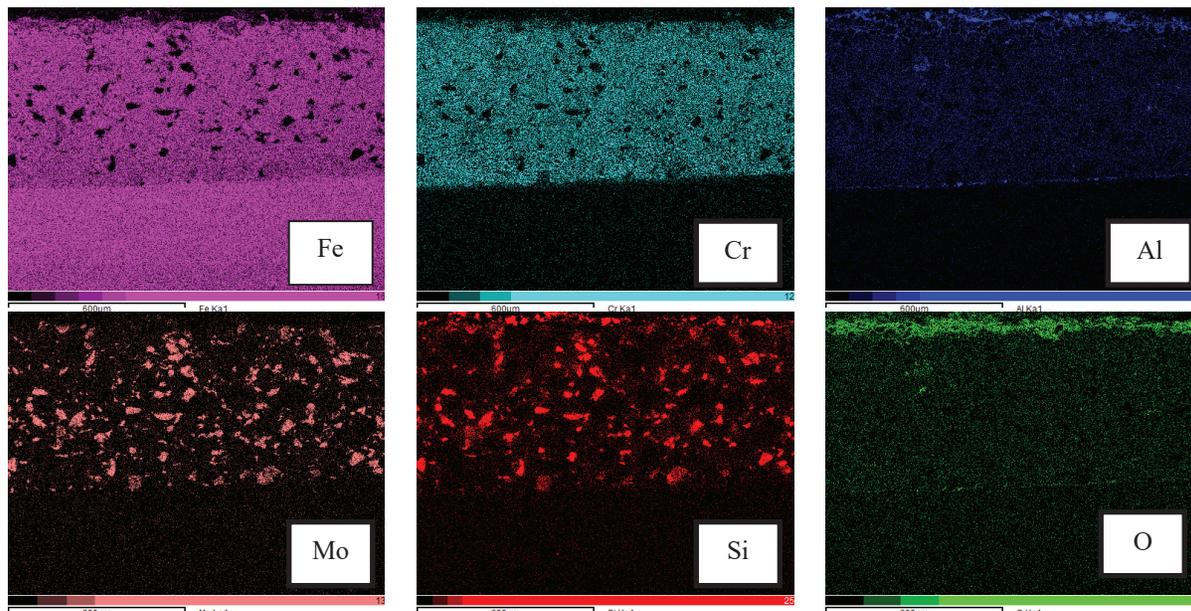


FIGURE 7. EDX elemental mapping of FeCrAlTiY-10 mass% MoSi₂ coating after corrosion test at 700°C for 8 cycles

In general, the chlorine attack leads to the formation metal chlorides that may be in the form of gas at high temperatures, resulting in weight loss. It can act as a catalyst for material deterioration and is often not easy to be observed due to its volatile nature. The volatile species of chlorides results in the development of cracks and pits, which provide easy path for the species to penetrate into the alloys [15]. This may be the reason why the detached area of corroded sample is severe compared to oxidized sample.

CONCLUSIONS

Based on the results obtained the SPS method significantly suppress the coating element oxidation during sample preparation. Additionally, the FeCrAlTiY-10 mass% MoSi₂ coating plays a role in improving the resistance of carbon steel toward oxidation and corrosion at high temperature. After oxidation test, a thin Al₂O₃ scale was formed on the coating surface, leading to high protection from environmental degradation. While, the presence of chlorine containing atmosphere promotes the mixed oxide formation consisting of (Cr,Fe)₂O₃, Al₂O₃, and Fe₃O₄.

ACKNOWLEDGEMENTS

The authors thank Mr. Ciswandi and Mr. Edi Sutiawan for technical support and discussion. The authors also acknowledge Research Center for Physics-Indonesian Institute of Sciences for providing characterization facilities. This work is partially supported by Program Unggulan 2018 of Indonesian Institute of Sciences.

REFERENCES

1. L. Pezzato, K. Brunelli, P. Dolcet, M. Dabalà, *Surface & Coatings Technology*, **307**, 73-80 (2016)
2. W. Yang, Q. Li, W. Liu, J. Liang, Z. Peng, B. Liu, *Vacuum*, **144**, 207-216 (2017)
3. B. Wielage, G. Reisel, A. Wank, G. Fritsche, Chemnitz / D, ITSC, Osaka, J, May 10th-12th (2004)
4. Y. Pan, S. Wang, *Ceramics International*, **44**, 19583-19589 (2018)
5. K. Kurokawa and A. Yamauchi, *Solid State Phenomena*, **127**, 227-232 (2007)
6. F. Zhang, L.T. Zhang, A.D. Shan, J.S. Wu, *Journal of Alloys and Compounds*, **422**, 308-312 (2006)
7. A. Afandi, R. Nisa, K.A.Z. Thosin, "Line profile analysis of ODS steels Fe20Cr5AlTiY milled powders at different Y₂O₃ concentrations", in *Journal of Physics, IOP : Conference Series*, **817**, 012028 (2017)
8. T. Sudiro, K.A.Z. Thosin, D. Aryanto, A.S. Wismogroho, K. Kurokawa, *Materials Science Forum*, **827**, 300-305 (2015)
9. L. Zhu, Y. Zhu, X. Ren, P. Zhang, J. Qiao, P. Feng, *Surface & Coatings Technology*, **375**, 773-781 (2019)

10. W. Chen, X. Shan, Y. Guo, J. Li, Z. Zou, F. Guo, X. Zhao, P. Xiao, [Surface & Coatings Technology](#), **357**, 841-848 (2019)
11. F. Golestani, M. Zakeri, M. Razavi, M.R. Rahimipour, M. Shirani, [Ceramics International](#), **44(7)**, 8403-8408 (2018)
12. J. Pane, D.H. Simbolon, B. Hermanto, A. Afandi, H. Izzuddin, K. Sebayang, M. Situmorang, T. Sudiro, *The Effects Of MoSi₂ Addition On High Temperature Oxidation Behavior Of Flame Sprayed FeCrAlTiY Coatings*. (Submitted to *Journal Protection of Metals and Physical Chemistry of Surface* at August 2019)
13. N.A. Rabbani, E.A. Basuki, T. Sudiro, A. Afandi, "Microstructure and oxidation resistance of spark plasma sintered Ytria-Zirconia ODS steels", [IOP Conf. Series: Materials Science and Engineering](#), **541**, 012028 (2019)
14. Y. Song, G. Jiang, Y. Chen, P. Zhao, Y. Tian, [Scientific Reports](#), **7(1)**, 1-13 (2017)
15. S.S. Kalsi and B. Singh, *International Journal on Emerging Technologies*, **7(1)**, 129-132 (2016)